

## Experimental Investigation On Surface Roughness Of Heat Treated Ti-6Al-4V Machined By WEDM

Lakhwant Singh<sup>1</sup> Sukhjinder Singh<sup>2</sup> Charanjit Singh Kalra<sup>3</sup>

*<sup>1</sup>Department of mechanical engineering,  
Dr. IT Group of Institutes, Banur, Punjab, India.*

*<sup>2</sup>Assistant professor, Punjabi university Patiala, Punjab, India.*

*<sup>3</sup>Assistant professor, SUSCET, Tangori, Punjab, India.*

### Abstract

In this study the Ti-6Al-4V is heat treated at 1100°C followed by water quenching to improve its hardness. Then the hardened specimens of Ti-6Al-4V is machined by WEDM on different process parameters. Experiments were conducted based on Taguchi's method and as per L<sub>25</sub>(5<sup>6</sup>) orthogonal array while considering six controllable factors (i.e. parameters), with five levels each. The surface roughness of all the specimens was examined with ITI-Surface roughness tester with 0.8 μm cutoff length. The important machining parameters of WEDM which effects the surface roughness is Pulse-On time, Pulse-off time, Peak current and Servo voltage. In this research WEDM experiment using 0.25 mm diameter brass wire is used for better Surface finish. SEM analysis has been done on the specimen with maximum surface roughness and minimum surface roughness

**Keywords:** Wire electrical discharge machining (WEDM), Surface roughness(Ra), Taguchi method.

### Introduction

Titanium and titanium alloys have a wide range of applications in aerospace, energetic, chemical and automobile industry. Some titanium alloys are excellent materials for biomedical use, especially as orthopedic alloys. The most important characteristic features of these biomedical titanium alloys are high strength, low density, excellent corrosion resistance and the best biocompatibility among the metallic biomaterials. The Ti-6Al-4V alloy, originally having been developed as a construction alloy for aircraft industry, belongs to the most significant alloys within the implant alloys for hard tissue replacement [1]. Ti-6Al-4V alloy has two allotropic phases, namely, the body centered cubic (BCC) structured β phase and the hexagonal close-packed (HCP) structured α phase. The β phase distributes along the boundaries of α phase. It contains 6% aluminum for a stabilization and 4% vanadium for β

stabilization, and when it is heated up to 882 °C, a phase transforms to  $\beta$  phase [2,3]. Within the family of titanium alloys, the  $\alpha+\beta$  alloys are the most widely used because of the great variety of microstructures and mechanical properties that can be obtained by varying their composition and thermo mechanical treatments [1]. One of these  $\alpha+\beta$  alloys has the greatest commercial importance namely Ti-6Al-4V, making up more than half of the sales of titanium alloys [2].

WEDM is a thermo- electrical process in which material is removed by a series of sparks between work piece and wire electrode (tool). The part and wire are immersed in a dielectric (electrically non conducting) fluid, usually deionized water, which also acts as a coolant and flushes the debris away. The material which is to be cut must be electrically conductive.

In WEDM, there is no direct contact between workpiece and tool(wire) as in conventional machining process, therefore materials of any hardness can be machined and minimum clamping pressure is required to hold the workpiece. In this process, the material is eroded by a series of discrete electrical discharges between the workpiece and tool. These discharges cause sparks and result in high temperatures instantaneously, up to about 10000° C. These temperatures are huge enough to melt and vaporize the workpiece metal and the eroded debris cools down swiftly in working liquid and flushed away, the working principle is shown in the figure 1.2. The effectiveness of the whole process depends on number of input process parameters such as pulse on time, pulse off time, servo voltage, peak current, dielectric flow rate, wire feed, and wire tension. The important machining responses include material removal rate (MRR), surface roughness (Ra), Kerf (width of cut), wire wear ratio (WWR) and surface integrity factors [5].

Dhruv.h Gajjar et al [6] found that pulse on time at level 3 (130  $\mu$ s), pulse off time at level 3 (60  $\mu$ s), servo voltage at level 2 (30volts) are the best process parameter for the MRR, KERF width and Surface roughness for machining of Ti-6Al-4V using WEDM. Pulse off time has opposite effect to pulse on time. MRR decrease with increase of pulse off time, while surface roughness reduces. Surface roughness reduces with increase of servo voltage. Vijaybabu.T et al [7] described an optimum cutting parameters for Titanium Grade5 (Ti-6Al-4V) using Wire-cut Electrical Machining Process (WEDM). The response of Volume Material Removal Rate (MRR) and Surface Roughness (Ra) were considered for improving the machining efficiency. It was observed that the pulse on time, and peak current are the most significant factors for the performance measures. The wire tension, servo voltage and servo feed settings are less significant on performance measure. Reham Reda et al.[8] studied the effect of water quenching on mechanical properties of cast Ti-6Al-4V alloy. Tensile, hardness and Charpy impact toughness tests were performed. The samples were heated up to different temperatures in  $\alpha+\beta$  range (900°C, 935°C, 980°C), then isothermally held for 10 minute, followed by water quenching. The results showed that the final properties of cast Ti-6Al-4V alloy are highly dependent on the quenching temperature. Mechanical properties of Ti-6Al-4V cast alloy are affected considerably by heat treatments and developed microstructures. Lokeswara Rao T. [9] Evaluated the effects on machining parameters on volume material removal rate, surface roughness on Titanium Grade5 (Ti-6Al-4V)

using Wire-cut Electrical Machining Process (WEDM). The Experimentation has been done by using Taguchi's L25 orthogonal array (OA) under different conditions like pulse on, pulse off, peak current, wire tension, servo voltage and servo feed settings. Regression equation is developed for the VMRR and Ra. Basil Kuriachen et al.[10] used two level full factorial techniques for modelling and predicting the surface roughness in WEDM of titanium (Ti-6Al-4V) alloy. The predicted values of surface roughness by the mathematical model were compared with the experimental values. The pulse on time, dielectric pressure, the interaction of voltage and pulse on time are significant parameters which affect the surface roughness. Minimum surface roughness can be obtained by adopting a low value of pulse on time (20  $\mu$ s) and a high value of dielectric pressure (15 kgf/cm<sup>2</sup>). Peter Pinke et al.[11] observed the influence of the solution treatment at 1050°C, 950°C and 800°C with water or air cooling followed by aging treatment at 550°C was investigated on the specimens from Ti-6Al-4V model titanium alloy. After the treatments 1050°C water and 950°C water  $\alpha'$  martensite structure was created, in the other cases a lamellar structure of  $\alpha + \beta$  phases was formed. The results obtained from experimental heat treatment of casted Ti-6Al-4V model alloy show that an  $\alpha'$  martensitic structure is formed after water cooling from the solution treatment at 1050 °C. After the water cooling from 800°C only an  $\alpha$  phase lamellar structure was created in the untransformed  $\beta$  phase. Martensite  $\alpha'$  structure did not appear. After water cooling from 950 °C  $\alpha'$  martensite structure with primary  $\alpha$  phase was formed. Air cooling from each solution temperature lead to lamellar structure of  $\alpha + \beta$  phases. The character of the formed microstructures has not changed basically after the aging treatment at 550°C. The highest growth of hardness compared with the initial hardness was detected after the heat treatment at 1050 C/1h/water + 550 °C/4h.

After detailed study of above mentioned different research papers it has been concluded that hardness of Ti-6Al-4V is increased by increasing the temperature up to 1100°C followed by water quenching as compared to other quenching methods. It is also observed that machining of heat treated hardened Ti-6Al-4V on WEDM was not performed by many researchers. So machining of heat treated hardened Ti-6Al-4V on WEDM is experimented in this research work. The process parameters of WEDM that were frequently used and found to be more influential than the rest were Pulse-On Time, Pulse-Off Time, Peak Current, Wire Feed Rate, Wire tension and Servo Voltage. Hence, these process parameters were studied in this research work.

**Experimental Procedure and Analysis**

Cold-rolled cylindrical plate of Ti-6Al-4V with a size of 40 mm diameter and 6 mm thickness was used in this study. The chemical compositions of Ti-6Al-4V are listed in Table 1.

**Table 1:** Chemical compositions of Ti-6Al-4V (mass%)

Element	Al	Fe	V	C	Ti
%	5.75	0.28	3.9	0.08	remaining

Hardness value of Ti-6Al-4V before heat treatment was checked using Rockwell hardness tester and mean was taken into account, which is 28 HRC. The samples were




**Results and Discussion**

After all the experimentations and measurements, it is required to study the effect of different machining parameters of WEDM for machining of heat treated Ti-6Al-4V. The effects of process parameters i.e. pulse on time, pulse off time, peak current, feed rate, wire tension and servo voltage on surface roughness on WEDM has been analyzed for exploring the research finding for the better combination of parameters and control over machining of Heat treated Ti-6Al-4V.

**Table 4:** Experimental result for Surface roughness(Ra)

RUN	T-On μs	T-Off μs	IP Amps	WT Kg- f	SV Volts	W F m/ min	Ra 1 (μm)	Ra 2 (μm)	Ra 3 (μm)	Ra mean (μm)
1	110	51	70	4	10	6	1.860	1.768	1.353	1.660
2	110	54	110	6	30	7	1.409	1.565	1.519	1.497
3	110	57	150	8	50	8	1.445	1.326	1.372	1.381
4	110	60	190	10	70	9	1.243	1.206	1.455	1.301
5	110	63	230	12	90	10	1.565	1.215	1.869	1.549
6	115	51	110	8	70	10	2.164	2.568	2.191	2.307
7	115	54	150	10	90	6	1.565	1.455	2.099	1.706
8	115	57	190	12	10	7	1.676	1.888	2.127	1.897
9	115	60	230	4	30	8	1.436	1.869	2.081	1.795
10	115	63	70	6	50	9	1.501	1.611	1.620	1.577
11	120	51	150	12	30	9	2.854	2.173	2.173	2.400
12	120	54	190	4	50	10	2.117	1.860	2.154	2.043
13	120	57	230	6	70	6	2.173	2.615	2.413	2.400
14	120	60	70	8	90	7	3.121	3.002	2.873	2.998
15	120	63	110	10	10	8	2.302	2.173	2.081	2.185
16	125	51	190	6	90	8	2.486	2.910	3.057	2.817
17	125	54	230	8	10	9	2.062	2.413	2.413	2.296
18	125	57	70	10	30	10	2.670	2.044	2.016	2.243
19	125	60	110	12	50	6	2.293	2.928	2.376	2.532
20	125	63	150	4	70	7	2.974	2.984	2.274	3.011
21	130	51	230	10	50	7	2.633	2.597	2.633	2.621
22	130	54	70	12	70	8	1.814	2.228	1.307	1.783
23	130	57	110	4	90	9	2.154	1.915	1.878	1.982
24	130	60	150	6	10	10	2.541	2.173	1.639	2.117
25	130	63	190	8	30	6	2.707	1.897	2.016	2.206

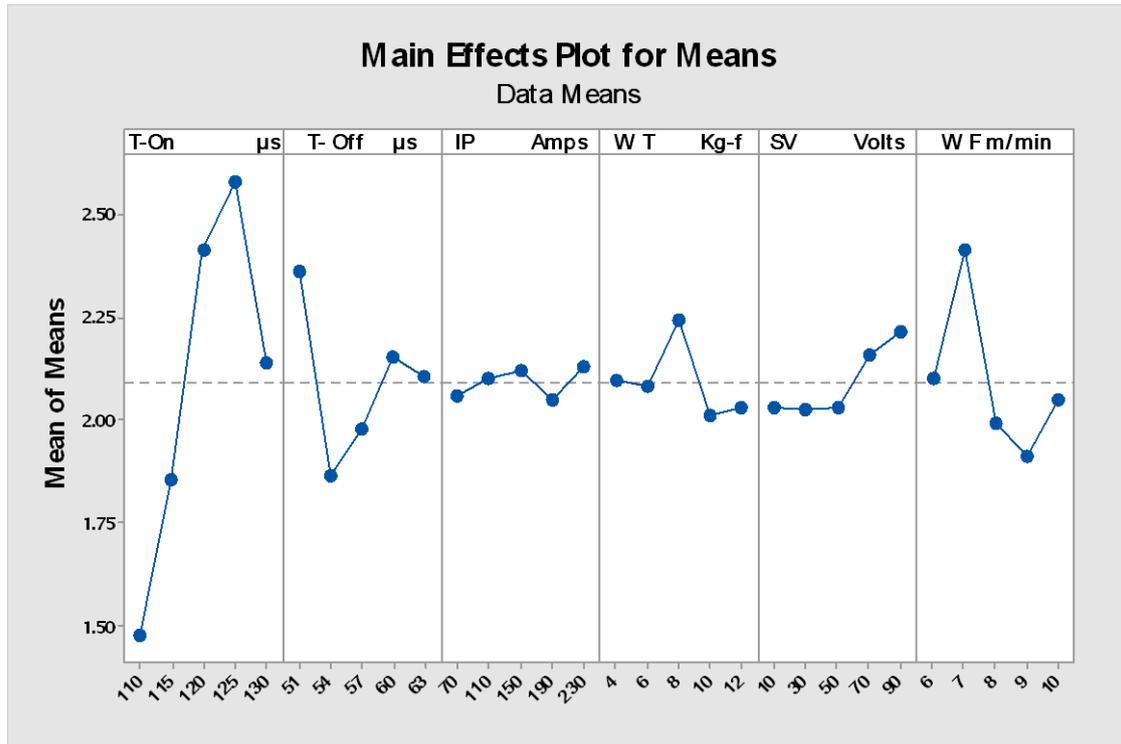

**Figure 2:** Response graph for means (Ra)



The Experimental results show the effect of six process parameters on surface roughness. Fig-4 shows the effect of surface roughness for the pulse on, pulse off, peak Current, wire tension and Servo Voltage by response graph for means (Ra). In Fig., it shows that with an increase of pulse on time the surface quality of the machined surfaces were decreased because under longer pulse time on the electrical sparks generate bigger craters on the surface of work piece.

**Table 5.5:** Response table for means (Ra)

Levels	T-On	T-Off	IP	WT	SV	WF
1	1.478	2.361	2.060	2.098	2.031	2.101
2	1.856	1.865	2.101	2.082	2.028	2.413
3	2.413	1.981	2.123	2.246	2.031	1.992
4	2.580	2.157	2.053	2.011	2.160	1.911
5	2.142	2.106	2.132	2.032	2.218	2.052
Delta	1.102	0.496	0.079	0.234	0.190	0.502
Rank	1.000	3.000	6.000	4.000	5.000	2.000

Table 5.5 shows the response table for means ranking of WEDM Parameters for better surface quality. It shows that the pulse on time has the highest effect on surface roughness of machined surfaces. The IP (peak current) has lowest effect on surface roughness of machined surface by WEDM

### Microstructure investigation

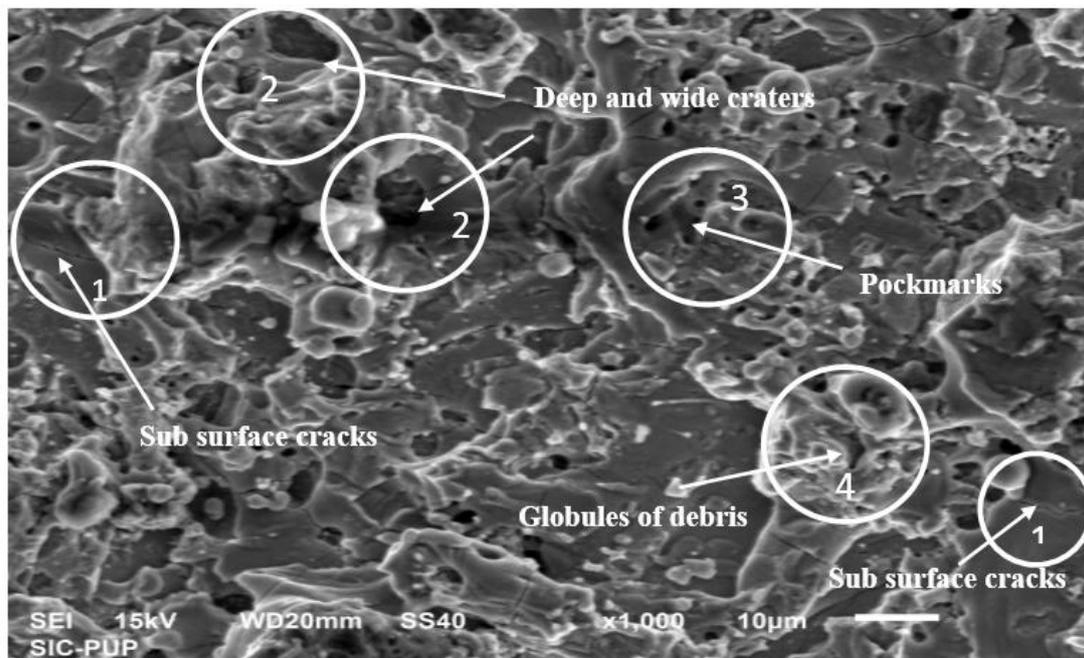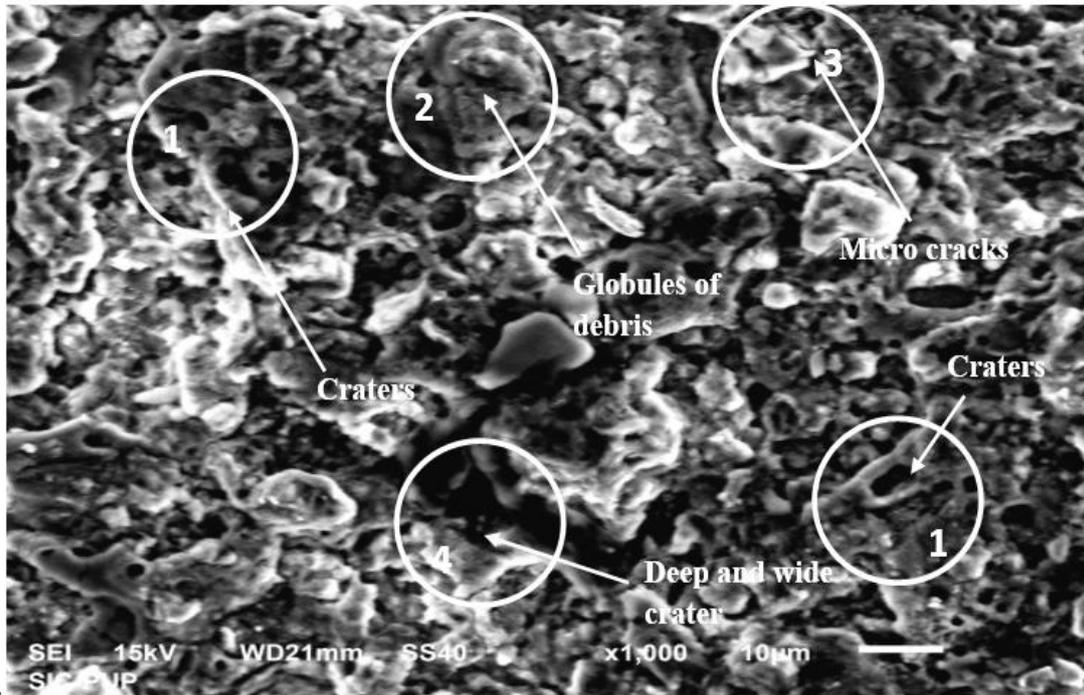

**Figure4:** SEM micrographs (1000x): Exp. No 20. , at T-on = 125 µs, T-off=63µs, IP = 150 A, SV = 70V, WF= 7 m/min, WT= 4 Kg-f.

After WEDM operations, the machined specimens were examined using scanning electron microscope (SEM). A SEM (JEOL, Tokyo, Japan, model JSM-6610LV) analysis of machined surfaces of pure titanium has major micro structural changes after WEDM. Figures show the SEM image of machined surface by WEDM process with better surface quality. In these figures, the wire electrode was oriented vertically, and the table fed from left to right. The surface topography presented in figure 1 revealed that surface maybe caused by an uneven fusing structure, globules of debris (marked as 2), craters (marked as 1), micro cracks (marked as 3), deep and wide crater is (marked as 4). Figure 2 show the micro graph of machined surface with less surface quality which shows that higher current equate to more thermal energy in the spark thus vaporizing and melting more of the workpiece material. This results in deep and wide craters (marked as 2) left in the surface of the workpiece. It should be noted that the sizes of the craters is effected by the amount of current that is allowed to pass through each of the sparks. The figure also reveals the globules of debris (marked as 4), pockmarks (marked as 3), Sub surface cracks (marked as 1) formation was usually associated with the development of high thermal stresses which exceeding the fracture strength, as well as with plastic deformation. In general, the density of cracks increases and more pronounces as the peak current and pulse duration was raised.

## Conclusion

In the presented work, experiments are carried out surface roughness with variables as pulse on time, pulse off time and servo voltage. There are 25 experimental readings taken for all variables to conduct the investigation. Finally it can be concluded that Surface quality decreases with increase of pulse on time because the increases of pulse on time produce crater with broader and deeper characteristic. Pulse off time has opposite effect to pulse on time while surface roughness increases with increase in Pulse off time. During off time removed material flushed away. More the off time better the flushing. Surface roughness reduces with increase of servo voltage because when smaller value is set, the mean gap becomes narrower, which leads to an increase in number of electric sparks.

## References

- [1] Williams D. F. In: Brunette D. M., Tengvall P., Textor M., Thomsen P. (eds.) Titanium in medicine, Springer-Verlag, Berlin, 2001, pp.13-24
- [2] Suresh N, Pillai M Gopalakrishna, Jose Mathew, "Investigations into the effects of electron beam welding on thick Ti-6Al-4V titanium alloy" J Mater Process Technol 2007;192-193.
- [3] Meshram Suresh D, Mohandas T, "A comparative evaluation of friction and electron beam welds of near-a titanium alloy" Mater Des 2010; 31:45-52.
- [4] Material science and engineering by William D. Callister, Jr. Department of Metallurgical Engineering The University of Utah.

- [5] Sreenivasa Rao M1, Venkaiah N2, “Review on Wire-Cut EDM Process. International Journal of Advanced Trends in Computer Science and Engineering” Vol.2 , No.6, Pages : 12-17 (2013)
- [6] Dhruv H. Gajjar, Jayesh V. Desai Optimization of MRR, “Surface Roughness and Kerf Width in wire EDM Using Molybdenum Wire” Volume.4, Issue:2,February:2015
- [7] Vijaybabu.T ,Dr.D.V.Ravishankar , Dr . Eshwara Prasad . Koorapati Parametric “Optimization of Wire Electrical Discharge Machining (WEDM) Process Using Taguchi Method” The International Journal Of Engineering And Science (IJES) || Volume || 3 || Issue || 11 || Pages || 52-58 || 2014 ||
- [8] Reham Reda, Adel A. Nofal , Abdel-Hamid A. Hussein, “Effect of Quenching Temperature on the Mechanical Properties of Cast Ti-6Al-4V Alloy” Journal of Metallurgical Engineering (ME) Volume 2 Issue 1, January 2013
- [9] Lokeswara Rao T., N. Selvaraj , “Optimization of WEDM Process Parameters on Titanium Alloy Using Taguchi Method” International Journal of Modern Engineering Research (IJMER), Vol. 3, Issue. 4, Jul. - Aug. 2013 pp-2281-2286
- [10] Basil Kuriachen, Dr. Josephkunju Paul, Dr.Jose Mathew, “Modeling of Wire Electrical Discharge Machining Parameters Using Titanium Alloy (Ti-6AL-4V)” International Journal of Emerging Technology and Advanced Engineering, ISSN 2250-2459, Volume 2, Issue 4, April 2012
- [11] Peter Pinke , Mihály Réger , “Heat treatment of castedTi-6Al-4V titanium alloy” project VEGA No. 1/1081/04
- [12] Kuriachen Basil, Dr. Josephkunju Paul, “ Jeju M.Issac, “Spark Gap Optimization of WEDM Process on Ti6Al4V” International Journal of Engineering Science and Innovative Technology (IJESIT) Volume 2, Issue 1, January 2013
- [13] Siva Prasad Arikatla, K. Tamil Mannan and Arkanti Krishnaiah, “Investigations on Surface Characterisation of Wire Electric Discharge Machined Surface of Titanium Alloy” International Journal of Engineering Research and Technology. ISSN 0974-3154 Volume 6, Number 4 (2013), pp. 663-570
- [14] Aniza Alias, Bulan Abdullaha, Norliana Mohd Abbasa , “WEDM: Influence of machine feed rate in machining titanium Ti-6Al-4V using brass wire and constant current(4A)” Procedia Engineering 41 ( 2012 ) 1812 – 1817
- [15] Rajeev Kumar and Shankar Singh, “Current Research Trends in Wire Electrical Discharge Machining: An Overview” International Journal on Emerging Technologies 3(1): 33-40(2012)
- [16] D. Satishkumar & M. Kanthababu & V. Vajjiravelu , “Investigation of wire electrical discharge machining characteristics of Al6063/SiCp composites” Int J Adv Manuf Technol (2011) 56:975–986
- [17] S. S. Mahapatra & Amar Patnaik, “Optimization of wire electrical discharge machining (WEDM) process parameters using Taguchi method” Int J Adv Manuf Technol (2007) 34:911–925

- [18] Tatsuro Morita, Kei Hatsuoka, Takashi Iizuka and Kazuhiro Kawasaki, “Strengthening of Ti–6Al–4V Alloy by Short-Time Duplex Heat Treatment” *Materials Transactions*, Vol. 46, No. 7 (2005) pp. 1681 to 1686
- [19] Nihat Tosun ,Can Cogun, Gul Tosun , “A study on kerf and material removal rate in wire electrical discharge machining based on Taguchi method” *Journal of Materials Processing Technology* 152 (2004) 316–322
- [20] M.T. Jovanovic´ , S. Tadic´, S. Zec, Z. Mis´kovic´, I. Bobic´, “The effect of annealing temperatures and cooling rates on microstructure and mechanical properties of investment cast Ti–6Al–4V alloy” *Materials and Design* 27 (2006) 192–199
- [21] N. Tosun, C. Cogun and H. Pihtili , “The Effect of Cutting Parameters on Wire Crater Sizes in Wire EDM” *Int J Adv Manuf Technol* (2003) 21:857–865.
- [22] Parveen Kr. Saini, Mukesh Verma,” Experimental Investigation of Wire-EDM Process Parameters on MRR of Ti-6al-4v Alloy”*International Journal of Innovative Technology and Exploring Engineering (IJITEE)* ISSN: 2278-3075, Volume-4, Issue-5, October2014